

# INTRODUCING PX5

## MODIFIED P20

*The High Performance  
Alternative for:*

**PLASTIC MOLDS**

**RUBBER MOLDS**

**PRESS PLATENS**

**DIES**

# KNOCK OUT

## THE COMPETITION



### *Features*

- Machines 30 to 50 percent faster than P20
- Pre-hardened to 29-33 HRC
- Uniform microstructure & hardness with extremely improved machined surface finish
- Never needs stress relieving
- Improved weldability and greatly reduced susceptibility to weld cracking
- Reduced surface-hardened layer in EDM making finishing operations easier



**DAIDO STEEL**

PX5 is distributed by  
Lindquist Steels, Inc.,  
a Daido partner company



**LINDQUIST STEELS, INC.**  
TOOL STEEL SPECIALISTS

[www.lindquiststeels.com](http://www.lindquiststeels.com)

*Corporate Office:* Lindquist Steels, Inc.  
1050 Woodend Road  
Stratford, CT 06615

800-243-9637 • FAX: 203-386-0132  
© Lindquist Steels, Inc. Copyright

Lindquist Steels, Inc.  
1950 Old Dunbar Road  
West Columbia, SC 29172  
800-845-7052 • FAX: 803-794-6658

# Chemical Composition


## General Chemistry

Material	Hardness	Chemical Composition (%)						AISI Grade
		C	S	Mn	Cr	Mo	V	
PX5	29-33HRC	.18	.04	1.75	2.20	.40	.10	P20 Modified

# Quality Characteristics I


## Materials / Mold Life

General purpose plastic molding material for mass production.

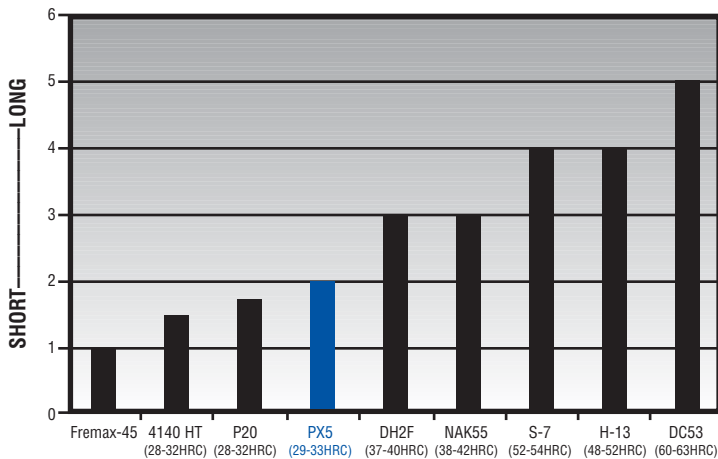

## Hardness Distribution

PX5 shows uniform hardness distribution through to the center.

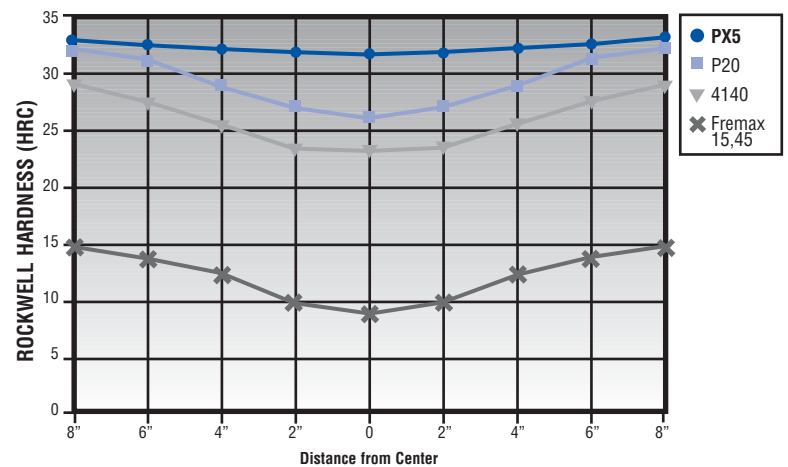


# Quality Characteristics II


## • Features - Isotropy and Uniform Strength

- PX5's strength is the same level at both the center and surface of the material and the isotropy (T/L) is at least 0.95.
- PX5 ranks in the highest toughness class among P20 materials

## Toughness

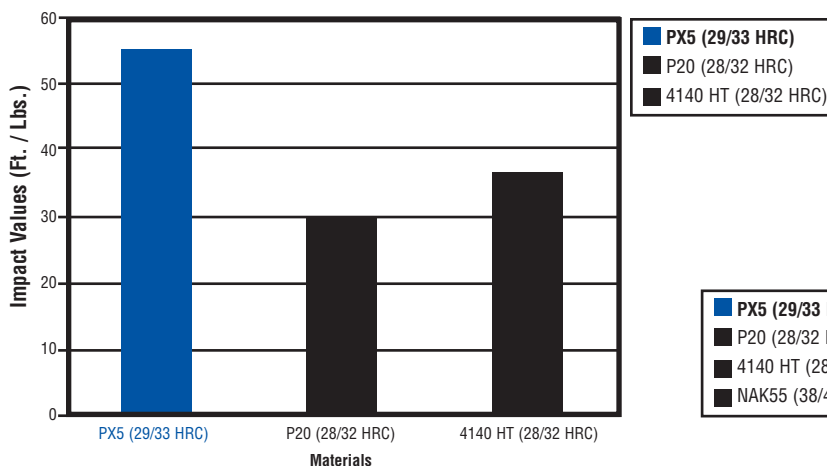


## Machining Characteristics

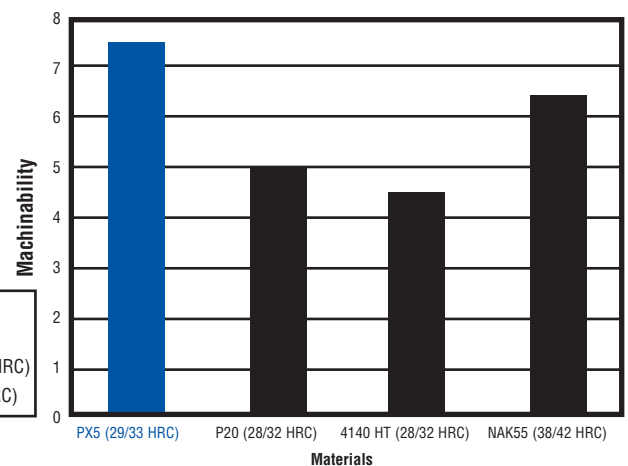

# Quality Characteristics III

## Tensile / Yield Properties

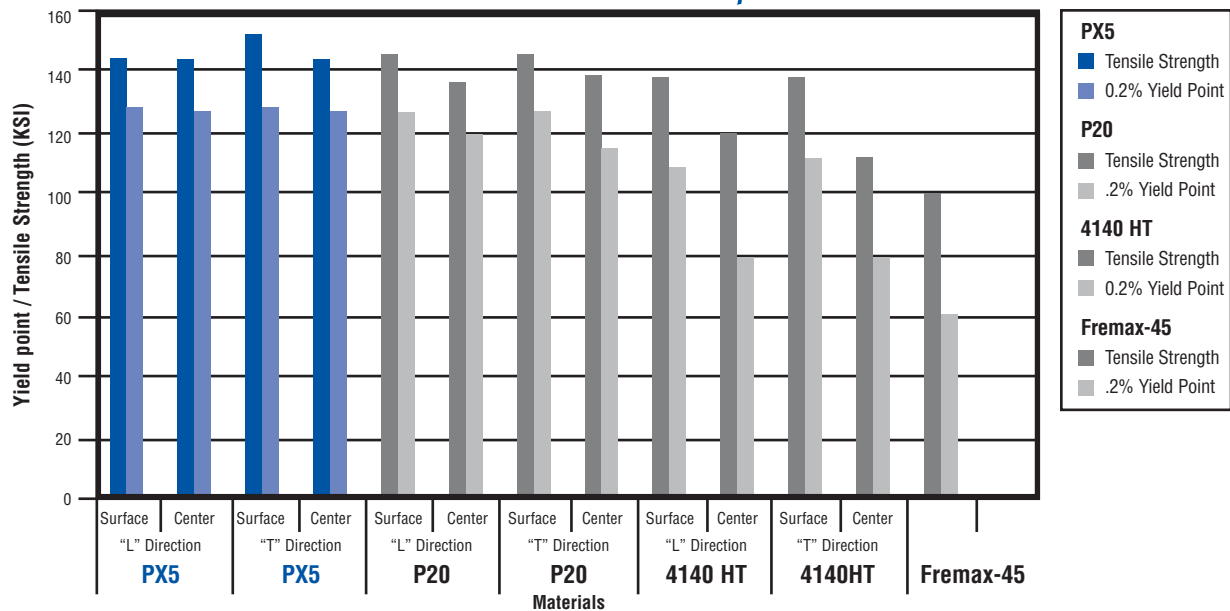

## Physical Properties

Thermal Conductivity (W/m • °C) (( ) cal/cm • sec • °C)

	20°C	100°C	200°C	300°C	400°C
PX5	42.45 (0.1014)	42.36 (0.1012)	42.07 (0.1005)	39.22 (0.0937)	38.80 (0.0927)
4140 HT	42.28 (0.1010)	41.61 (0.0994)	42.70 (0.1020)	39.39 (0.0941)	38.00 (0.0908)
P20		48.30 (0.1153)	41.50 (0.0991)	38.60 (0.0921)	38.10 (0.0910)

Coefficient of Thermal Expansion (x 10<sup>-6</sup>/°C)

	30 ~ 100°C	30~ 200°C	30~ 300°C	30~ 400°C	30~ 600°C
PX5	11.9	12.7	13.1	13.5	14.1
4140 HT	11.9	12.7	13.2	13.7	14.2
P20	11.9	12.3	12.7	12.8	13.7

Specific Heat (J/kg • °C) (( ) cal/g • °C)

	20°C	100°C	200°C	300°C	400°C
PX5	481.40 (0.115)	489.80 (0.117)	540.00 (0.129)	552.60 (0.132)	627.90 (0.150)
4140 HT	481.40 (0.115)	514.90 (0.123)	581.90 (0.139)	590.20 (0.141)	607.00 (0.145)
P20	460.20 (0.109)	477.20 (0.114)	493.90 (0.118)	527.40 (0.126)	786.90 (0.188)

Young's Modulus (Mpa) (( ) kfg/mm<sup>2</sup>)


	20°C	100°C	200°C	300°C	400°C
PX5	207,482 (21,150)	204,048 (20,800)	198,162 (20,200)	192,276 (19,600)	184,919 (18,850)
4140 HT	206,991 (21,100)	203,067 (20,700)	197,672 (20,150)	190,314 (19,400)	181,976 (18,550)
P20	205,863 (20,985)	202,532 (20,645)	200,471 (20,092)	191,686 (19,539)	184,902 (18,898)

# Welding Characteristics

## • PX5 and Conventional Knowledge on Weld Cracking

- PX5 is an alloy designed to decrease weld crack susceptibility. Thus, it is possible to lower the pre- and post-heat temperature from the conventional range of 300°C - 500°C to 200°C.

### Weld Cracking Sensitivity

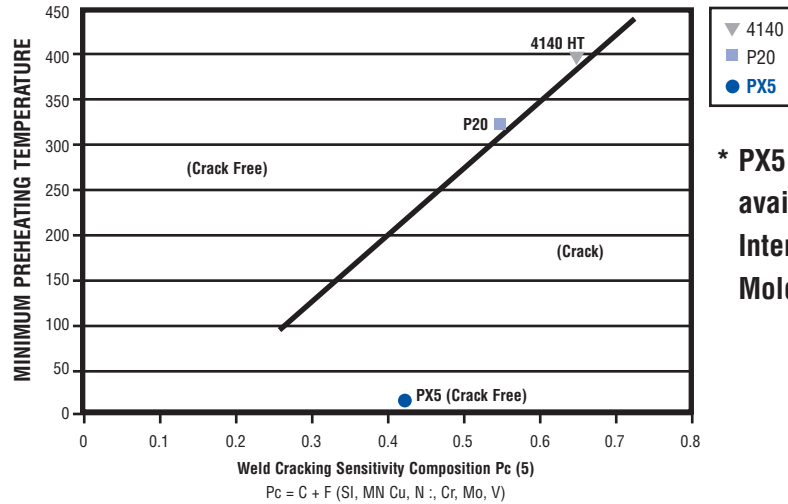


\* PX5 Weld Rod is available from International Mold Steel.

## • Hardness of Welded Area

- PX5's maximum hardness on the heat affected area is the lowest among the P20-type materials. Thus, the susceptibility for fracture is low and cutting and grinding operations are carried out more easily.

### Hardness Distribution Around the Weld

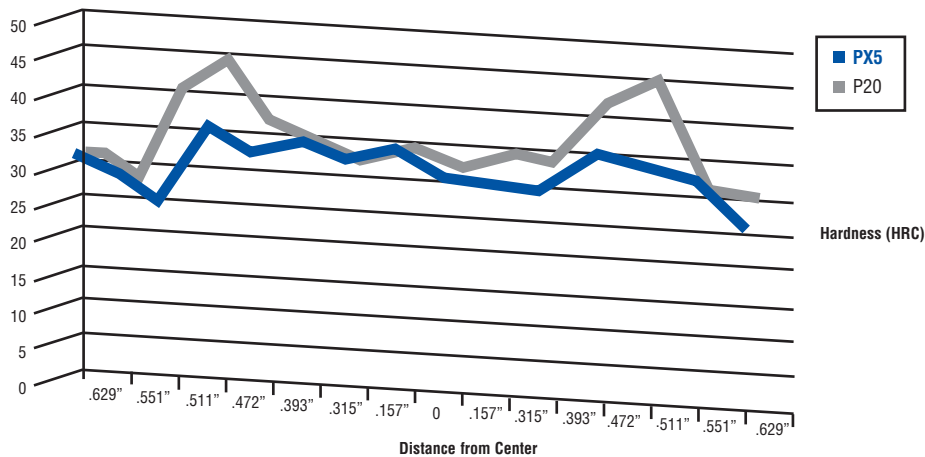

INTERNATIONAL MOLD STEEL, INC.  
www.imsteel.com

**LINDQUIST STEELS, INC.**  
TOOL STEEL SPECIALISTS  
www.lindquiststeels.com

Corporate Office: Lindquist Steels, Inc.  
1050 Woodend Road  
Stratford, CT 06615  
800-243-9637 • FAX: 203-386-0132

Lindquist Steels, Inc.  
1950 Old Dunbar Road  
West Columbia, SC 29172  
800-845-7052 • FAX: 803-794-6658

Daido Steel Limited and Lindquist Steels, Inc. shall not be held responsible for damage caused by misunderstanding or improper use of the technical information contained in this brochure. The contents of this brochure may be subject to change without notice. Please inquire for the latest information. No portion of this brochure may be reproduced without the express permission of Daido Steel Limited and International Mold Steel, Inc.